

UNCLASSIFIED

AD 279 138

*Reproduced
by the*

ARMED SERVICES TECHNICAL INFORMATION AGENCY
ARLINGTON HALL STATION
ARLINGTON 12, VIRGINIA



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

NOLTR 61-153

CATALOGED BY ASTIA
AS AD No. 279138

A LOW GASSING IGNITER MIXTURE FOR
VARIOUS PYROTECHNIC DELAY
COMPOSITIONS

- RELEASED TO ASTIA
BY THE NAVAL ORDNANCE LABORATORY
- ☒ Without restrictions
 - ☐ For Release to Military and Government Agencies Only.
 - ☐ Approval by BuWeps required for release to contractors.
 - ☐ Approval by BuWeps required for all subsequent release.

1 NOVEMBER 1961

NOL

UNITED STATES NAVAL ORDNANCE LABORATORY, WHITE OAK, MARYLAND

279 138

NOLTR 61-153




A LOW GASSING IGNITER MIXTURE FOR
VARIOUS PYROTECHNIC DELAY COMPOSITIONS

Prepared by:

E. Eugene Kilmer

Approved by:


Chief, Explosion Dynamics Division

ABSTRACT: Mixes of zirconium and lead monoxide have been investigated for use as hot wire sensitive gasless igniter mixes for igniting gasless delay powders. A (50/50) zirconium/lead monoxide composition is sensitive to hot wire ignition; it reliably initiates molybdenum and manganese base delay mixtures; it acts essentially as a gasless delay igniter for such delay mixtures used in systems having delays up to several seconds in time. It does not act gasless when igniting long burning tungsten delay mixes. It will not satisfactorily ignite all delay compositions so that its selection for use must be based on knowledge of its specific behavior with the particular delay composition contemplated.

PUBLISHED DECEMBER 1961

Explosions Research Department
U. S. NAVAL ORDNANCE LABORATORY
WHITE OAK, MARYLAND

NOLTR 61-153

1 November 1961

This report presents information concerning the search for a "gasless" igniter to be used in electro-explosive devices. The work was carried out in the Explosion Dynamics Division of the Explosions Research Department, U. S. Naval Ordnance Laboratory, White Oak, Maryland, in connection with Wep Task RUME 3E000/212 1/F008 10 004, Problem 016, Applied Research for Underwater Detonators. The results of this investigation are intended for the information and use of the Naval Ordnance Laboratory and should be of interest to others working with electro-explosive devices.

W. D. COLEMAN
Captain, USN
Commander


C. J. ARONSON
By direction

CONTENTS

	Page
Introduction.	1
Selection and Preparation of Mixes.	2
Selection of Final Mix for Further Tests.	2
Testing in Delay Devices.	3
Sensitivity to Hot Wire Ignition.	4
Conclusions	5
References.	6

ILLUSTRATIONS

Figures	Title	Page
1	Light Output During Burning of Several Zirconium/Lead Monoxide Ignition Mixtures . . .	10
2	The Test Vehicle Used for Testing the Fast Burning Delay Compositions	11
3	The Test Vehicle Used for Testing the Slow Burning Delay Composition.	12
4	Percent Firing vs. Constant Current for Zr/PbO 50/50 Igniter Mix	13

Tables

1	Preliminary Tests of Firing Voltages for Zr/PbO Compositions.	7
2	Observed Delay Times for Delay Compositions Ignited from (50/50) Zirconium/Lead Monoxide Igniter Mixture.	8
3	Determination of the Firing Characteristics of Igniter Mix (50/50) Zr/PbO by the Bruceton Sensitivity Method.	9

A LOW GASSING IGNITER MIXTURE FOR
VARIOUS PYROTECHNIC DELAY COMPOSITIONS

Introduction

1. The designs of electro-explosive devices (EEDs) containing "gasless" delays have almost exclusively used primary explosives heated by a bridgewire to effect initial reaction. Primary explosives, when they react, produce liberal quantities of gaseous combustion products. If these gases are allowed to materially increase the internal pressure of the EED, the burning rate of the gasless delay, which is pressure sensitive, is considerably increased over its rate at ambient pressure, and inefficient use of the delay (with respect to time/length) results. In addition, if the internal gas pressure is not controlled, time uniformity may not be obtained.
2. To overcome these difficulties practical designs have allowed for venting the primary explosive gases through vent holes to the exterior or have incorporated a fully contained internal vent chamber (1). The former expedient reduces the shelf life of the EED in moist environments and also prevents potting of the EED. The latter solution overcomes the moisture and potting difficulties but requires increased volume or length (for the vent chamber) and this space in a weapon system is often at a premium.
3. Another method of overcoming the problem would be to eliminate the primary explosive and substitute an igniter material sensitive to ignition by a hot wire and having combustion products which are essentially gasless. Such igniter materials have not been generally available. Two possibilities, however, exist:

Metal acetylides.

"Gasless" mixes similar to the gasless delays but with sufficient sensitivity to be initiated by hot wires.

The acetylides had been previously investigated (2) but abandoned because of their extreme static sensitivity and difficulty of preparation. Gasless igniter materials of sufficient sensitivity were unknown; however, some gasless igniter mixes, A-1A for example (3), were known to be marginally close to the sensitivity desired*

*A-1A could be initiated by a hot wire some of the time but not always. In some cases the wire could be burned out without initiating the A-1A.

4. The Universal Match Corporation in 1959 was assigned a problem under Contract NOrd 13466, Task 2, to develop hot wire sensitive gasless igniter mixes for use in non-vented delay systems. The results of their work are summarized in their final contract summary report (4). In brief, they found a number of mixes which could be ignited by hot wires. They centered their testing on the most promising; mixes of boron and lead dioxide and mixes of zirconium and lead dioxide. The boron mix was found to introduce appreciable non-uniform delays itself so zirconium/lead dioxide was the final igniter material selected. When it was used in non-vented delays appreciable reduction in time over the vented system resulted.

5. The work reported herein is a continuation of the work started at the Universal Match Corporation. It was hoped to obtain a sensitive gasless igniter capable of being incorporated into non-vented delays without appreciably decreasing the burning time below that of identical vented items. It has been found that a (50/50) zirconium/lead monoxide igniter mix acts as if it were gasless when igniting molybdenum and manganese base mixes in systems with delays up to several seconds. This mix, however, does not satisfactorily ignite all delay compositions and affects the burning times of long burning tungsten base delays in obturated systems.

Selection and Preparation of Mixes

6. After reviewing the work performed by the Universal Match Corporation and all other pertinent literature and information, it was decided that mixtures of zirconium and lead monoxide would be investigated. An approximate stoichiometric mixture of these ingredients, (17/83) Zr/PbO, as well as several oxygen deficient combinations were prepared. The zirconium powder conformed to specification JAN-Z-399A. The lead monoxide was reagent grade obtained from Merck and Co. It was finer than 325 mesh. For reasons of safety, mixing was performed with the ingredients wet. The wetting fluid was ethyl acetate. Quantities of 10 grams or less were wetted with the fluid and mixed in a Waring blender for twenty minutes. The mixtures were then filtered and dried in an oven.

Selection of Final Mix for Further Tests

7. The selection of the final mix for further testing was based on two criteria:

The ignition sensitivity at a selected size hot wire.

The rapidity of the combustion sensed by a phototube detector.

Preliminary sensitivity tests were conducted by pressing the mixtures about a 0.0004-inch diameter Tophet-C wire, 0.050 inch long, and then determining, by a few exploratory tests, the potential needed on a 1-microfarad capacitor to cause samples to fire. The results of this testing are given in Table 1. From this table it can be seen that the (20/80), and (50/50) Zr/PbO mixes could be ignited without sufficient difference in sensitivity to choose between them. The (95/5) Zr/PbO mix could not be fired even at 6 microfarads and 250 volts, and was thus eliminated.

8. The (20/80), (40/60), and (50/50) Zr/PbO mixes were then subjected to hot wire ignition testing in which the light output was viewed as a function of time using a photoelectric detector tube and an oscilloscope. Typical traces for the three mixes are shown in Figure 1. The (20/80) Zr/PbO mix showed no output for the full sweep of the oscilloscope, which was 5 milliseconds in these tests, although the mix, of course, was ignited. The inherent delay was felt to be too long and the burning, which finally did occur, too erratic for further consideration of this mix as an igniter material. The (40/60) mixture and the (50/50) mixture ignited within the sweep time; however, the (40/60) mixture showed a rather slow build-up in intensity while the (50/50) mixture showed an even, rapid build-up to its final intensity. On the basis of these results it was decided to use only the (50/50) mixture for further testing.

Testing in Delay Devices

9. Tests in delay devices, both obturated and vented, were conducted with delay mixes of various burning rates. Comparisons were made between burning times in the vented and non-vented devices. Two types of test vehicles were chosen for these tests.

For the obturated condition the fast burning compositions (molybdenum and manganese based mixes (5), (6)) were tested in the unit shown in Figure 2, and the slow burning composition (tungsten based mix (5)) was tested in a larger body shown in Figure 3. The test devices were loaded such that there was no internal free volume for venting of gases during burning.

The vented devices were identical to the obturated ones shown in Figures 2 and 3 except that the charge holder was reduced in diameter and a vent hole 0.025 inch in diameter was drilled in the delay body slightly above the igniter level to allow gases to escape to the exterior.

10. On the basis of preliminary tests, the igniter mix was loaded at 10,000 psi. The initiator assembly contained 30 milligrams of (50/50) Zr/PbO igniter mix. The quantity of igniter used for the fast burning molybdenum and manganese base mixes was 100 milligrams while the slow burning tungsten base delay composition required 250 milligrams of the igniter mix. The delay compositions were loaded at 30,000 psi and the units tested over a temperature range of -65°F to $+160^{\circ}\text{F}$. The energy from a 1-microfarad capacitor charged to 60 volts was used to produce ignition and the ability of the mixture to ignite the delay compositions and the delay times were determined. Table 2 summarizes the results observed.

The manganese delay compositions were reliably initiated over the temperature range $+160^{\circ}\text{F}$ to -65°F in both the obturated and vented systems.

In the case of the molybdenum base delays, there was no significant difference in the observed delay times between the obturated and vented systems.

For the manganese delay compositions there was a small reduction of the burning time in the obturated system.

The slow burning tungsten base delay composition was ignited satisfactorily in the obturated system but in the vented system failures occurred at the igniter-delay mix interface. The failures were probably due in part to the loss of pressure caused by the venting. There was a considerable reduction in time in the obturated system as compared to the vented system. This can be seen from the tests conducted at 160°F where all items ignited properly. The table shows also that ignition reliability at the igniter-delay interface is a function of the operating temperature.

Sensitivity to Hot Wire Ignition

11. Two methods were used to determine the sensitivity of the (50/50) zirconium/lead monoxide mix to ignition by a hot wire.

The first was a capacitor discharge Bruceton type test (7) using a fixed 1-microfarad capacitor and a variable potential.

The second was a variable-amplitude, constant-current, run-down type test.

12. The data for the capacitor discharge test are shown in Table 3. The mean firing potential was determined to be 57.4 volts which corresponds to an energy of 16,500 ergs. If the assumed log normal distribution is correct, the 99.9% firing point is at 63.1 volts corresponding to an energy of 19,900 ergs.

13. The constant-current data were obtained on two groups of elements containing the igniter mix. The results are shown in graphical form in Figure 4. From this curve it can be seen that the current characteristics of the two groups were rather uniform, that virtually no primers fire below approximately 340 milliamperes, and that virtually all can be expected to fire above 420 milliamperes. The number at each point plotted on the curves indicates the number of igniters tested at this point.

Conclusions

14. From the experiments conducted it is concluded that the (50/50) zirconium/lead monoxide igniter mix acts as if it were "gasless" when igniting molybdenum and manganese base mixes having times up to several seconds. When igniting long burning tungsten base delays, there is an appreciable reduction of time in the obturated system over that of the vented system.

15. This igniter mix does not satisfactorily ignite all delay compositions; auxiliary igniters such as A-1A on top of the delay column may be necessary in some cases. The igniter mix may be satisfactorily ignited from hot wires. The energy required is somewhat more than that needed for sensitive primary explosives.

REFERENCES

- (1) NavOrd Report 5724, "An Investigation of Internal Venting for Delay Actuators", H. S. Leopold and E. E. Kilmer, 10 Sep 1957, Confidential
- (2) NOLM 10487, "Development of Gasless Delays for Low Energy Electric Primers", Progress Report (NOL-26-Re2b-222-5), W. W. Rymer, 15 Nov 1949
- (3) NavOrd OS 8976, "Powder Ignition, Gasless", 13 Nov 1959
- (4) Universal Match Corp., "Contract NOrd 13466, Task 2, Summary Report No. 3", Period 1 Jan 1958 to 30 Apr 1961, Confidential
- (5) Universal Match Corp., "Contract NOrd 13466, Task 2, Summary Report No. 2", Period 1 Dec 1955 to 1 Jan 1958, Confidential
- (6) MIL-M-21383-NOrd, "Manganese Delay Composition", 28 Apr 1958; and NavOrd OD 9360, "Preparation of Manganese Delay Composition", 5 May 1956
- (7) Princeton University, Statistical Research Group, "Statistical Analysis for a New Procedure in Sensitivity Experiments", AMP Report No. 101.1R SRG No. 40, Jul 1944

Table 1
Preliminary Tests of Firing Voltages
for Zr/PbO Compositions

Zr/PbO Weight Ratio	Loading Pressure (psi)	Capacitance (mfd)	Potential (volts)	Result*
95/5	10,000	6	250	Failure
50/50	10,000	1	48-50	Fire
50/50	20,000	1	53-54	Fire
40/60	10,000	1	48-50	Fire
40/60	20,000	1	53	Fire
20/80	10,000	1	50-65	Fire
20/80	20,000	1	60-65	Fire

* The lower voltage is the lowest value at which any sample was observed to fire.
The upper voltage is the lowest value at which all samples tested fired.

Table 2
Observed Delay Times for Delay Compositions
Ignited from (50/50) Zirconium/Lead Monoxide-Igniter Mixture

Type of Delay Powder	Inverse Burning Rate (sec/in)	Delay Column Length (inches)	Calculated Delay Time (seconds)	Temp. (°F)	OBTURATED		VENTED	
					Sample Size	Mean Delay Time (seconds)	Sample Size	Mean Delay Time (seconds)
Molybdenum base	0.22	0.270	0.059	165°F	5	0.0654	5	0.0661
	0.22	0.270	0.059	Room	5	0.0716	5	0.0710
	0.22	0.270	0.059	-65°F	5	0.0825	5	0.0805
Manganese base	2.53	0.233	0.589	160°F	10	0.519	10	0.539
	8.02	0.243	1.949	160°F	10	1.50	10	1.84
	13.23	0.265	3.51	160°F	10	2.54	10	2.79
	2.53	0.233	0.589	Room	10	0.565	10	0.578
	8.02	0.243	1.949	Room	10	1.63	10	1.89
	13.23	0.265	3.51	Room	10	2.66	10	2.77
Tungsten base	2.53	0.233	0.589	-65°F	10	0.585	10	0.674
	8.02	0.243	1.949	-65°F	10	1.62	10	1.99
	13.23	0.265	3.510	-65°F	10	2.82	10	2.95
	39.4	0.822	32.39	160°F	10	15.41	10	31.55
	39.4	0.822	32.39	Room	10	17.25	10	*
	39.4	0.822	32.39	-65°F	10	19.34	10	**

* 7/10 failed at the igniter-delay interface.

**10/10 failed at the igniter-delay interface.

Table 3

Determination of the Firing Characteristics of
Igniter Mix (50/50) Zr/PbO by the Bruceton Sensitivity Method

i	Volts h_i	n_i		in_i	i^2	$i^2 n_i$									
		Fire X's	Failure O's												
6	61	1	0	0	36	0									
5	60	3	1	5	25	25									
4	59	4	3	12	16	48									
3	58	7	4	12	9	36									
2	57	5	7	14	4	28									
1	56	5	5	5	1	5									
0	55	0	5	5	0	0									
c=log h_0 =1.74036		Sum	Sum	Sum=A		Sum=B									
d=Δlog h=0.007		Nx = 25	No = 25	A = 53											
			No2= 625	A2= 2809		B = 142									
$m = c + d \left(\frac{A}{N_x} - \frac{1}{2} \right) \text{ or } = c + d \left(\frac{A}{N_o} + \frac{1}{2} \right)$ $m = 1.74036 + .007 \left(\frac{53}{25} + \frac{1}{2} \right) = 1.75870$ <p>Antilog m = 57.4 Volts</p> <table><tr><td>$M = \frac{NB-A^2}{N^2}$ Use Nx or No as above</td><td>From Table or Graph p. 51-54</td><td>$\delta = d(0.05 + 1.6M)$</td></tr><tr><td>$M = \frac{25(142)-2809}{625} = 1.186$</td><td>AMP Report No. 101.1R</td><td>$\delta = .007(.05+1.6(1.186))$</td></tr><tr><td></td><td></td><td>$\delta = 0.01363$</td></tr></table>							$M = \frac{NB-A^2}{N^2}$ Use Nx or No as above	From Table or Graph p. 51-54	$\delta = d(0.05 + 1.6M)$	$M = \frac{25(142)-2809}{625} = 1.186$	AMP Report No. 101.1R	$\delta = .007(.05+1.6(1.186))$			$\delta = 0.01363$
$M = \frac{NB-A^2}{N^2}$ Use Nx or No as above	From Table or Graph p. 51-54	$\delta = d(0.05 + 1.6M)$													
$M = \frac{25(142)-2809}{625} = 1.186$	AMP Report No. 101.1R	$\delta = .007(.05+1.6(1.186))$													
		$\delta = 0.01363$													
Prob. Firing	K	Kδ	m+Kδ	E (% point) =5CV ² *											
.001	-3.090	-0.042117	1.71658	5(1)(52.0) ² =13,520											
.500				5(1)(57.4) ² =16,470											
.999	+3.090	+0.042117	1.80082	5(1)(63.1) ² =19,910											

*C - microfarads
V - volts
E - ergs

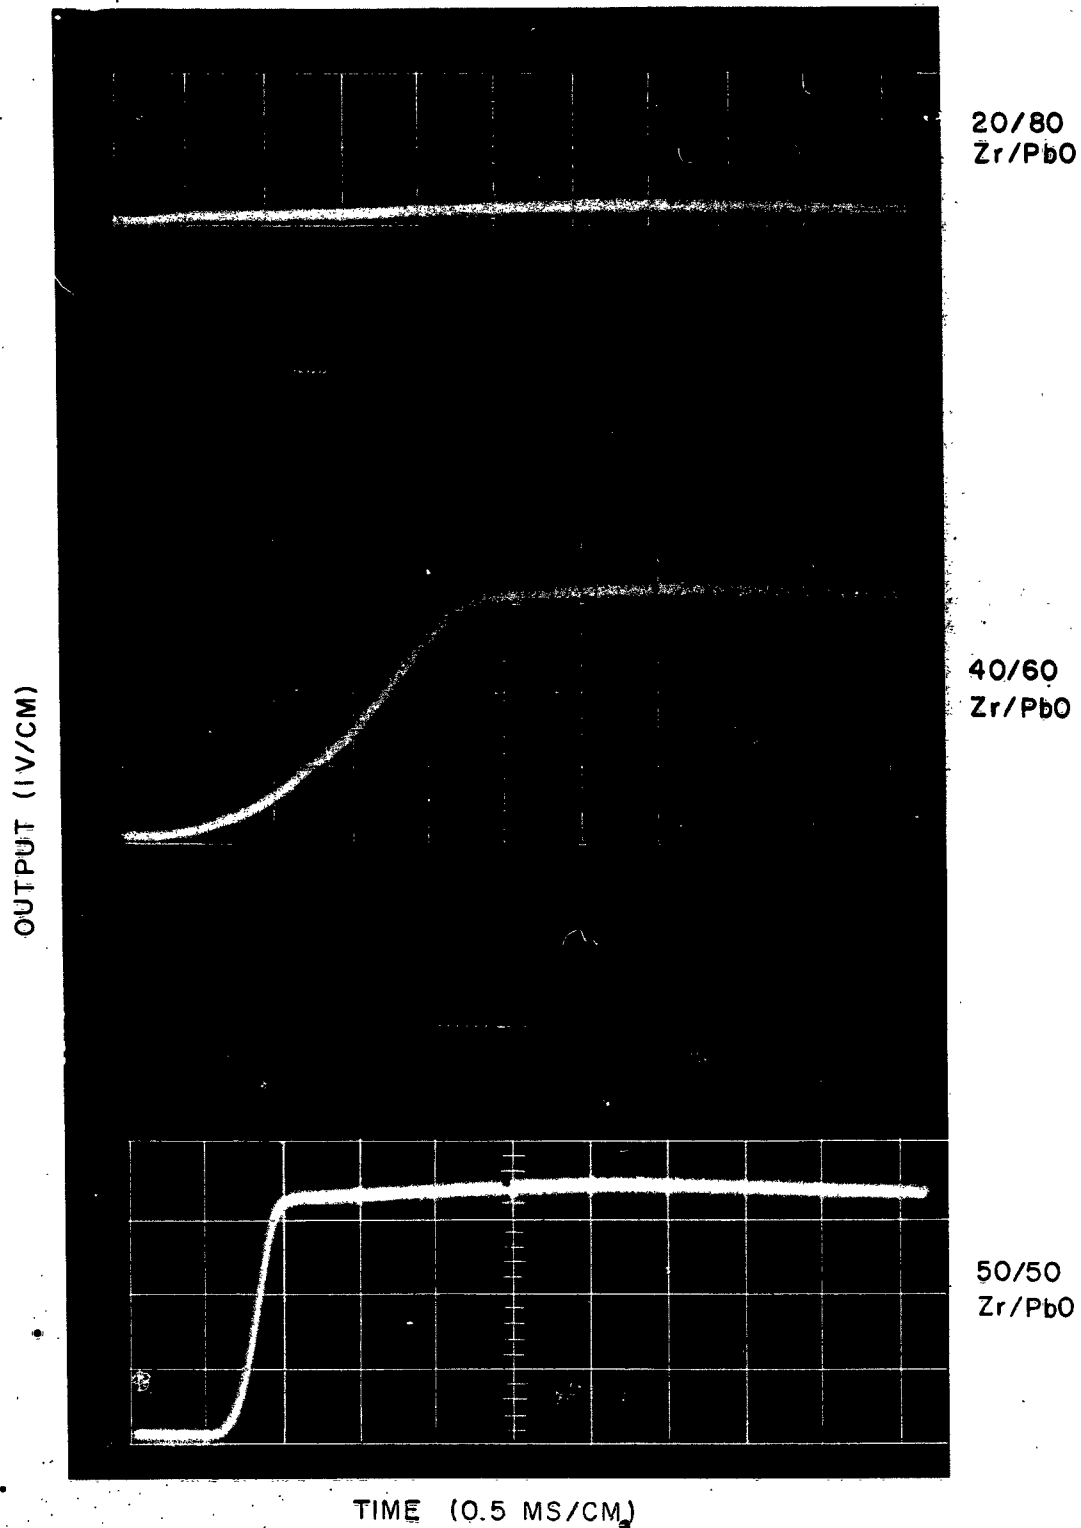


FIG. 1 LIGHT OUTPUT DURING BURNING OF SEVERAL ZIRCONIUM/LEAD MONOXIDE IGNITION MIXTURES

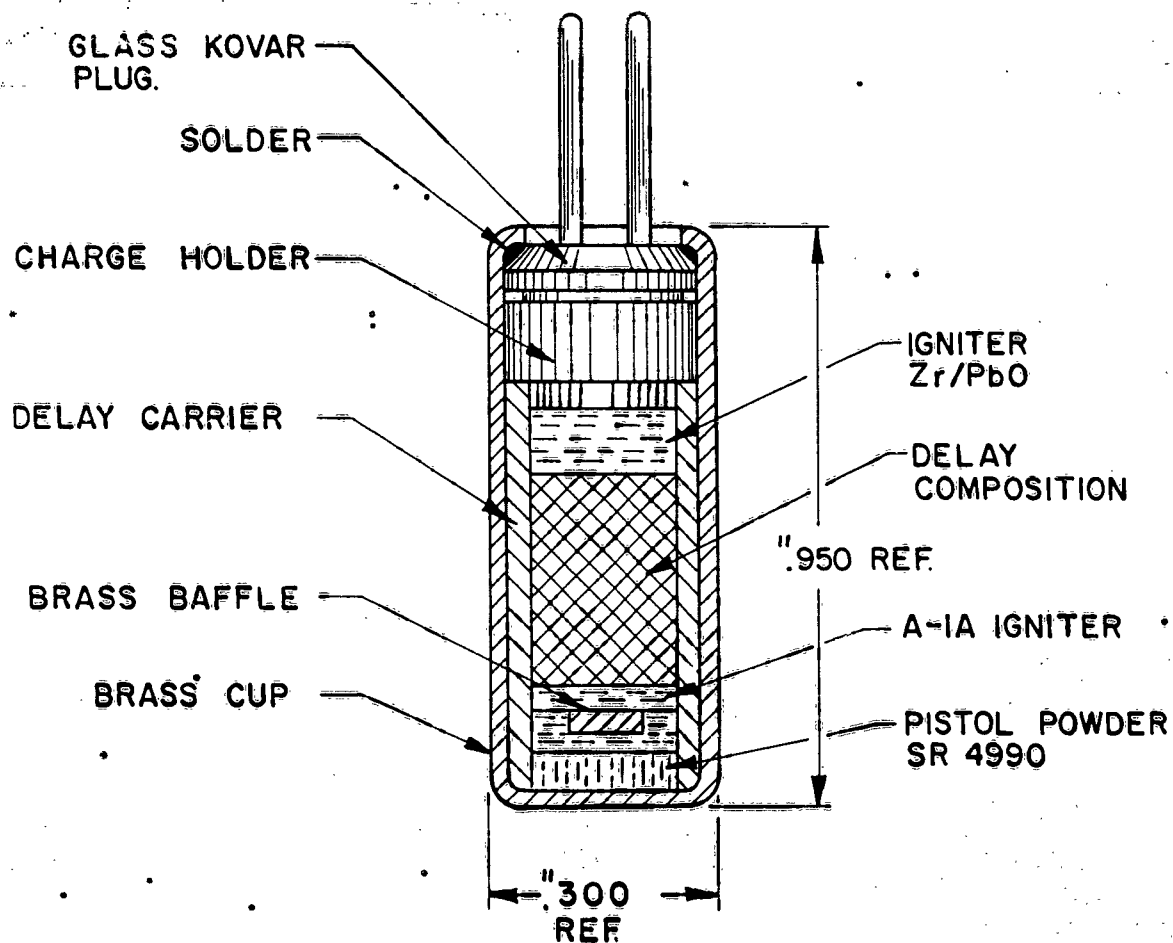


FIGURE 2. THE TEST VEHICLE USED FOR TESTING THE FAST BURNING DELAY COMPOSITIONS.

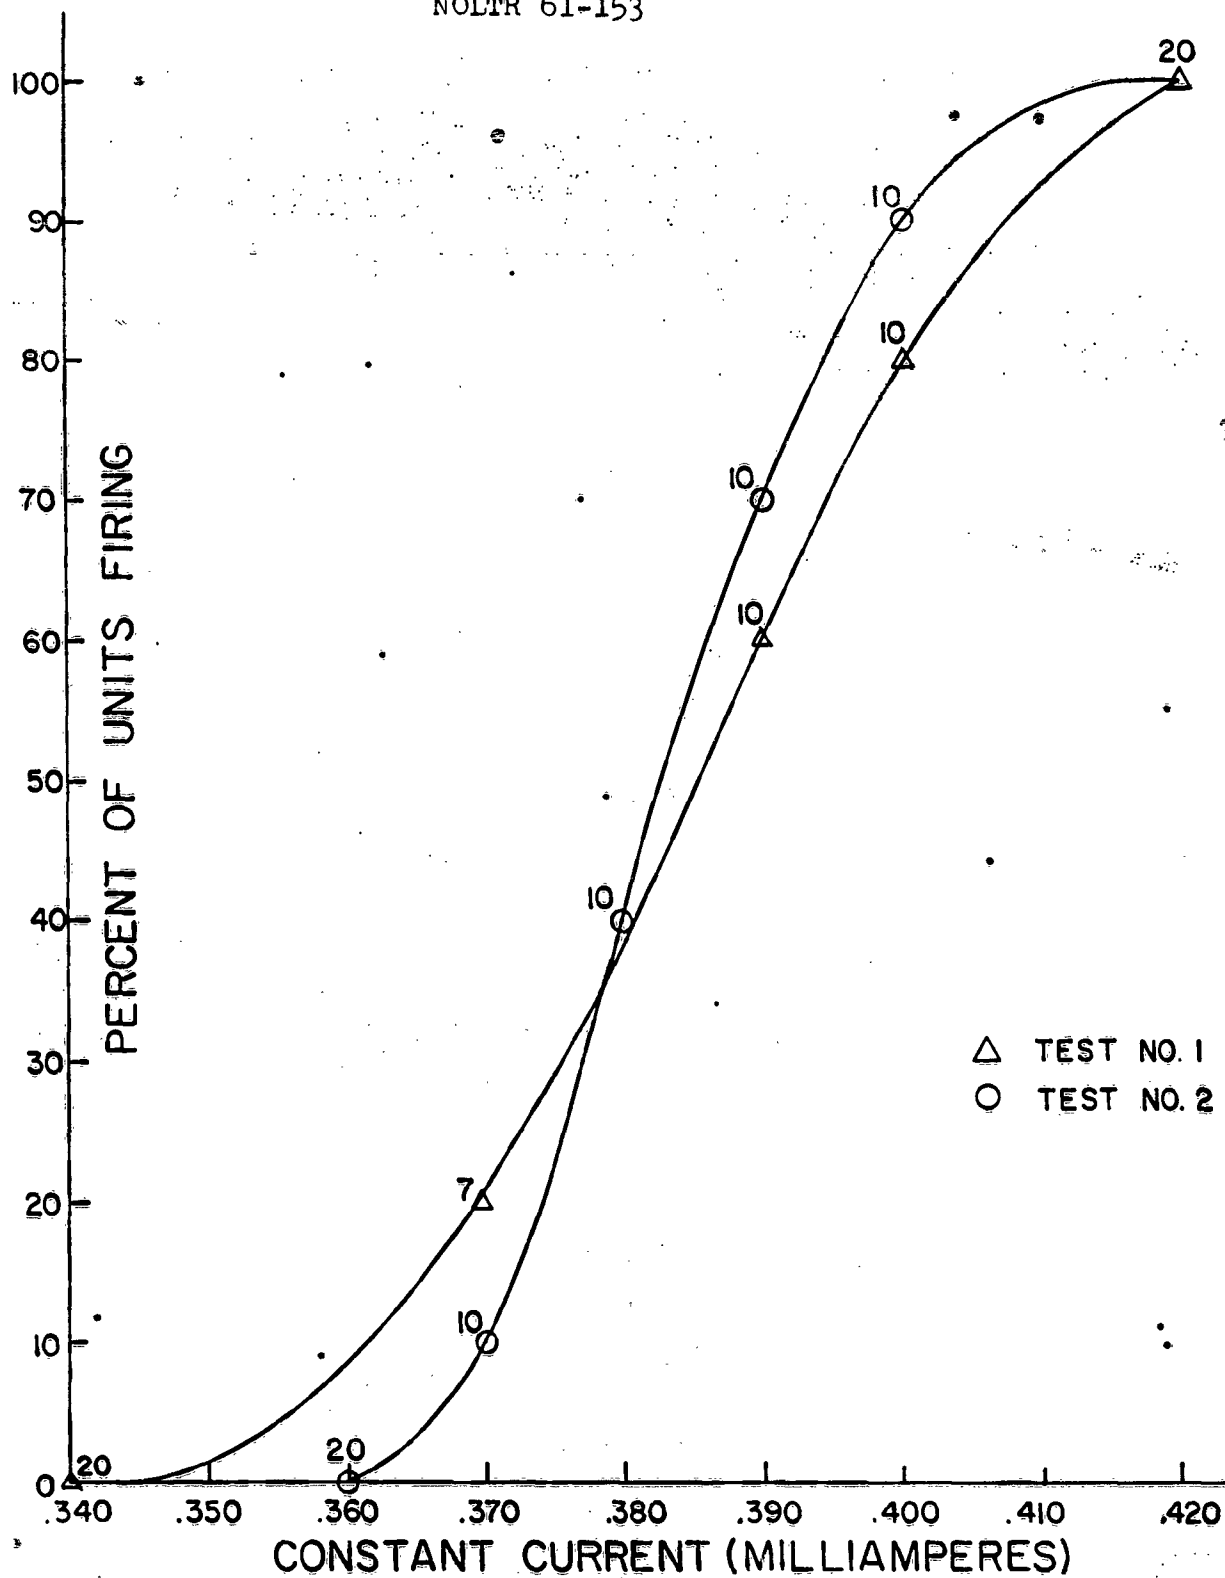


FIGURE 4. PERCENT FIRING VS CONSTANT CURRENT FOR Zr/PbO 50/50 IGNITER MIX.

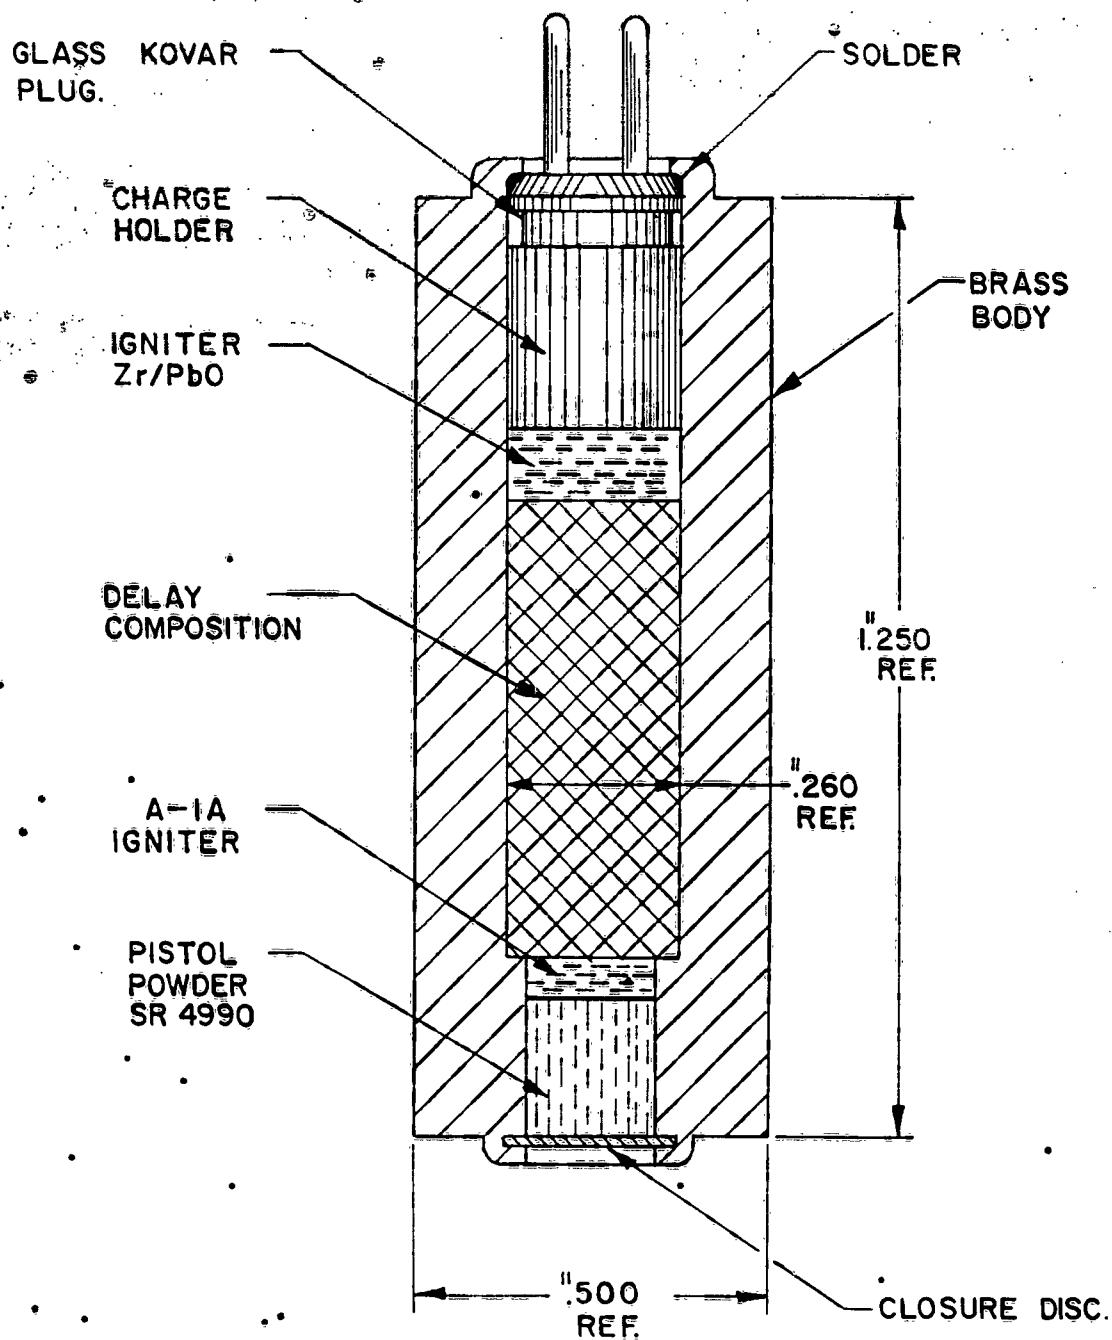


FIGURE 3. THE TEST VEHICLE USED FOR TESTING THE SLOW BURNING DELAY COMPOSITION.

DISTRIBUTION LIST

	Copies
Chief, Bureau of Naval Weapons	
Department of the Navy	
Washington 25, D. C.	
DIS-3	1
RUME-3	1
RUME-32	1
RMMO-2	1
RREN-312	1
 Director	
Special Projects Office	
Washington 25, D. C.	
SP-20	1
 Chief of Naval Research	
Department of the Navy	
Washington 25, D. C.	
Chemistry Branch	2
 Commander	
U. S. Naval Ordnance Test Station	
China Lake, California	
Code 556	1
Technical Library	2
B. A. Breslow	1
J. Sherman	1
 Director	
Naval Research Laboratory	
Washington 25, D. C.	
Technical Information Section	2
 Superintendent	
Naval Post Graduate School	
Monterey, California	1
 Commander	
Naval Air Development Center	
Johnsville, Pennsylvania	
Aviation Armament Laboratory	1
 Commander	
U. S. Naval Weapons Laboratory	
Dahlgren, Virginia	
Technical Library	2

Copies

Commanding Officer
U. S. Naval Weapons Station
Yorktown, Virginia
R & D Division

2

Commanding Officer
U. S. Naval Ordnance Laboratory
Corona, California
R. Hillyer

1

1

Commanding Officer
U. S. Naval Propellant Plant
Indian Head, Maryland
Technical Library
EODTC

1

1

Commanding Officer
U. S. Naval Ordnance Plant
Macon, Georgia

1

Commanding Officer
U. S. Naval Ammunition Depot
McAlester, Oklahoma
R. E. Halpern

1

Commanding Officer
U. S. Naval Underwater Ordnance Station
Newport, Rhode Island

1

Commanding Officer
U. S. Naval Weapons Evaluation Facility
Kirtland Air Force Base
Albuquerque, New Mexico

1

Commanding Officer
Naval Ammunition Depot
Crane, Indiana

1

Commanding Officer
U. S. Naval Ammunition Depot
Navy Six Six (66)
c/o Fleet Post Office
San Francisco, California

1

Commanding Officer
Naval Torpedo Station
Keyport, Washington

1

Copies

Office of Chief of Engineers
Department of the Army
Washington 25, D. C.

ENGNEB
ENGEB

1
1

Chief of Ordnance
Department of the Army
Washington 25, D. C.

ORDGU
ORDTB
ORDTN

1
1
1

Commanding General
Picatinny Arsenal
Dover, New Jersey

ORDBB-TH8
ORDBB-TJ1
ORDBB-TK3
ORDBB-TM1
ORDBB-TP1
ORDBB-TP2
ORDBB-TP3
ORDBB-TR2
ORDBB-TS1

1
1
1
1
1
1
1
1
1

Commanding Officer
Diamond Ordnance Fuze Laboratory
Connecticut Ave. & Van Ness St, N. W.
Washington 25, D. C.

Ordnance Development Laboratory
M. Lipnick (Code 005)
R. Comyn (Code 710)
G. Keehn (Code 320)

1
1
1
1

Commanding Officer
Office of Ordnance Research
Box CM, Duke Station
Durham, North Carolina

1

Commanding Officer
Rock Island Arsenal
Rock Island, Illinois

1

Commanding Officer
Engineer Research & Development Laboratory
U. S. Army
Ft. Belvoir, Virginia
Technical Intelligence Branch

1

Copies

Commanding Officer
Fort Dietrick
Maryland

1

Commanding General
U. S. Army Proving Ground
Aberdeen, Maryland
BRL

1

Commanding General
Frankford Arsenal
Philadelphia, Pennsylvania
S. Picoli

1

Commanding General
Redstone Arsenal
Huntsville, Alabama
Technical Library

1

Commander
Ordnance Corps
Lake City Arsenal
Independence, Missouri
Industrial Engineering Division

1

Chief of Staff
U. S. Air Force
Washington 25, D. C.
AFORD-AR

1

Commander
Wright Air Development Center
Wright-Patterson Air Force Base
Dayton, Ohio

1

Headquarters, Air Proving Ground Center
U. S. Air Force, ARDC
Eglin Air Force Base, Florida
PGTRI, Technical Library

1

Commander
Air Research & Development Command
Andrews Air Force Base
Washington 25, D. C.

1

Chief
Defense Atomic Support Agency
Washington 25, D. C.

2

Copies

Armed Services Technical Information Agency
Arlington Hall Station
Arlington, Virginia
TIPDR

10

Atomic Energy Commission
Washington 25, D. C.
DMA

1

Lawrence Radiation Laboratory
University of California
P. O. Box 808
Livermore, California
Technical Information Division

1

Director
Los Alamos Scientific Laboratory
P. O. Box 1663
Los Alamos, New Mexico
Library

1

Director
Applied Physics Laboratory
Johns Hopkins University
8621 Georgia Avenue
Silver Spring, Maryland
Solid Propellants Agency

1

1

Sandia Corporation
P. O. Box 5400
Albuquerque, New Mexico

1

Sandia Corporation
P. O. Box 969
Livermore, California

1

Commander
Holsten Ordnance Works
U. S. Army
Kingsport, Tennessee
Dr. R. Robbins

1

The Franklin Institute
20th & Benjamin Franklin Parkway
Philadelphia, Pennsylvania

1

Lockheed Aircraft Corporation
P. O. Box 504
Sunnyvale, California
Mr. J. Lightfoot

1

Naval Ordnance Laboratory, White Oak, Md.
(NOL technical report 61-153)
A LOW GASSING IGNITER MIXTURE FOR VARIOUS
PYROTECHNIC DELAY COMPOSITIONS (U), by E.
Eugene Kilmer. 1 Nov. 1961. 13p. charts,
tables. Project RUME 3E000/212 1/FO08 10
004, Problem 016.
Mixes of zirconium and lead monoxide have
been investigated as hot wire sensitive gas-
less igniter for igniting gasless delay pow-
ders. A (50/50) zirconium/lead monoxide com-
position is sensitive to hot wire ignition;
it initiates molybdenum and manganese base
delay mixtures; acts as a gasless delay ig-
niter for delay mixtures. It will not satis-
factorily ignite all delay compositions so
selection must be based on knowledge of spe-
cific behavior.

1. Pyrotechnics
2. Igniters
3. Delay mixture:
4. Zirconium
5. Lead monoxide
6. Molybdenum
7. Manganese
- I. Title
- II. Kilmer,
E. Eugene
- III. Project

1. Pyrotechnics
2. Igniters
3. Delay mixtures:
4. Zirconium
5. Lead monoxide
6. Molybdenum
7. Manganese
- I. Title
- II. Kilmer,
E. Eugene
- III. Project

Naval Ordnance Laboratory, White Oak, Md.
(NOL technical report 61-153)
A LOW GASSING IGNITER MIXTURE FOR VARIOUS
PYROTECHNIC DELAY COMPOSITIONS (U), by E.
Eugene Kilmer. 1 Nov. 1961. 13p. charts,
tables. Project RUME 3E000/212 1/FO08 10
004, Problem 016.
Mixes of zirconium and lead monoxide have
been investigated as hot wire sensitive gas-
less igniter for igniting gasless delay pow-
ders. A (50/50) zirconium/lead monoxide com-
position is sensitive to hot wire ignition;
it initiates molybdenum and manganese base
delay mixtures; acts as a gasless delay ig-
niter for delay mixtures. It will not satis-
factorily ignite all delay compositions so
selection must be based on knowledge of spe-
cific behavior.

Naval Ordnance Laboratory, White Oak, Md.
(NOL technical report 61-153)
A LOW GASSING IGNITER MIXTURE FOR VARIOUS
PYROTECHNIC DELAY COMPOSITIONS (U), by E.
Eugene Kilmer. 1 Nov. 1961. 13p. charts,
tables. Project RUME 3E000/212 1/FO08 10
004, Problem 016.
Mixes of zirconium and lead monoxide have
been investigated as hot wire sensitive gas-
less igniter for igniting gasless delay pow-
ders. A (50/50) zirconium/lead monoxide com-
position is sensitive to hot wire ignition;
it initiates molybdenum and manganese base
delay mixtures; acts as a gasless delay ig-
niter for delay mixtures. It will not satis-
factorily ignite all delay compositions so
selection must be based on knowledge of spe-
cific behavior.

1. Pyrotechnics
2. Igniters
3. Delay mixtures
4. Zirconium
5. Lead monoxide
6. Molybdenum
7. Manganese
- I. Title
- II. Kilmer,
E. Eugene
- III. Project

1. Pyrotechnics
2. Igniters
3. Delay mixture:
4. Zirconium
5. Lead monoxide
6. Molybdenum
7. Manganese
- I. Title
- II. Kilmer,
E. Eugene
- III. Project

Naval Ordnance Laboratory, White Oak, Md.
(NOL technical report 61-153)
A LOW GASSING IGNITER MIXTURE FOR VARIOUS
PYROTECHNIC DELAY COMPOSITIONS (U), by E.
Eugene Kilmer. 1 Nov. 1961. 13p. charts,
tables. Project RUME 3E000/212 1/FO08 10
004, Problem 016.
Mixes of zirconium and lead monoxide have
been investigated as hot wire sensitive gas-
less igniter for igniting gasless delay pow-
ders. A (50/50) zirconium/lead monoxide com-
position is sensitive to hot wire ignition;
it initiates molybdenum and manganese base
delay mixtures; acts as a gasless delay ig-
niter for delay mixtures. It will not satis-
factorily ignite all delay compositions so
selection must be based on knowledge of spe-
cific behavior.